



# Evaluation of Moisture Transfer to Improve the Conservation of Tiles Finishing Facades

Silvia Erba, Bruno Daniotti, Elisabetta Rosina, Antonio Sansonetti  
and Riccardo Paolini

**Abstract** The research of methodologies and tools to improve the durability of building components has the aim to find out the strategies to increase the service life, minimizing the environmental impacts. The paper refers on clinker facades, especially after the repairs of mortars due to severe damages. The authors achieved on-site investigations on a prominent study case in Leonardo Campus, at Politecnico di Milano, and laboratory tests to study the interaction between moisture and cement mortars, the decay effects, and the protective treatments to improve the mortar durability. The research sharpens the methods for the evaluation of water absorption and moisture transfer in external building components and proposes possible strategies of intervention. The methodology focuses on the characterization of the water behavior in mortars by different tests, the experiments in laboratory on mortars samples, to study the hygroscopic and capillarity absorption properties, and on site, through visual analysis and nondestructive techniques. The researchers studied a water-repellent protective treatment to apply on the finishing surface and evaluated it in terms of water-repellent efficacy, compatibility with the substrate, vapor permeability, and color stability. The investigations provide input data, useful for simulating the moisture transfer, validating the experimentations, and modeling the physical mechanisms, which occur on the façade. In addition, the method

---

S. Erba (✉) · B. Daniotti · E. Rosina · R. Paolini  
Politecnico Di Milano, Milan, Italy  
e-mail: [silvia.erba@polimi.it](mailto:silvia.erba@polimi.it)

B. Daniotti  
e-mail: [bruno.daniotti@polimi.it](mailto:bruno.daniotti@polimi.it)

E. Rosina  
e-mail: [elisabetta.rosina@polimi.it](mailto:elisabetta.rosina@polimi.it)

R. Paolini  
e-mail: [riccardo.paolini@polimi.it](mailto:riccardo.paolini@polimi.it)

A. Sansonetti  
Consiglio Nazionale delle Ricerche, Istituto per la Conservazione e Valorizzazione dei Beni Culturali (National Research Council, Department for the Conservation and Valorization of Cultural Heritage), Milan, Italy  
e-mail: [a.sansonetti@icvbc.cnr.it](mailto:a.sansonetti@icvbc.cnr.it)

24 analyses also the optical characteristics of the surface, with the aim to detect any  
25 change due to the application of further protective treatments and for aging process.

26 **Keywords** Moisture · Cements · Mortars · Water-repellent treatment · Durability

## 27 1 Introduction

28 The research of methodologies and tools to improve the durability of building  
29 components aims to find strategies to increase the service life, minimizing the  
30 environmental impacts (Nicolella 2003).

31 For existing buildings, the *residual service life* is the time span remaining after  
32 considering a specific moment. To assess the residual service life of an inspected  
33 building or component is crucial to reconstruct its *conservation history*, i.e., data on  
34 the original performance values, information on the installation, maintenance,  
35 trends of deterioration, etc.; several difficulties and the lack of information  
36 regarding the initial state prevent the complete achievement of this task. The pro-  
37 cess of assessment of the residual service life allows also to plan the remaining part  
38 of the service life, the performance levels to maintain equal or higher than the  
39 accepted threshold of the decreased service (Daniotti 2009).

40 As regards the listed contemporary buildings, a mandatory issue drives to the  
41 preservation of the original materials and features, together with keeping the  
42 residual service life of their components and system; therefore, the preservation  
43 criterion overcomes the functional criterion of maintaining the performance level by  
44 replacing the components before the end of their service life.

45 Therefore, the evaluation of risk factors and damage processes is the most  
46 important step for preventing decay, planning the effective routines for the early  
47 detection of anomalies, and constantly protecting the weakest part of the system.

48 The paper refers to a research aimed at improving the durability of clinker  
49 facades, especially after the repairs of mortars after severe damages. The authors  
50 achieved on-site investigations on an important study case in Milan and laboratory  
51 tests to study the interaction between the moisture and cement mortars, the decay  
52 effects, and the treatments to improve the mortar durability.

## 53 2 Planning Conservation Works in Humid Environment

54 The facades cladding is composed of cement mortar layers on which clinker tiles  
55 are applied. Therefore, the complete system of finishing includes the superimpo-  
56 sition of mortar layers with different compositions and surface morphology.  
57 Moreover, the line between the tiles edges and the mortar constitutes a possible gap  
58 in the outer layer and therefore a vulnerable line for the infiltration of water, and it  
59 increases the risk of triggering damages.

60 The application of water-repellent treatments on the mortar is a new frontier for  
61 the conservation plans of cultural heritage. The protective treatment has the  
62 requirement to guarantee a hydrophobic performance, reducing the presence of  
63 water on the surface and near-surface regions. At the same time, a proper protective  
64 layer guarantees the water vapor permeability (Amoroso and Fassina 1983). These  
65 treatments slow the transformations of the materials due to the decay processes,  
66 caused by aggressive external agents, and the imbalances in the boundary  
67 conditions.

68 The researchers tested two different mortar mix designs based on cement, per-  
69 forming several tests to evaluate the water transport phenomena and the radiation  
70 properties. At a second step, they applied a water-repellent polymeric treatment on  
71 the mortar surface; after an appropriate curing time, they repeated the same tests.

72 In other words, the authors evaluated the water-repellent effectiveness through a  
73 series of laboratory tests and computer-based simulations, including the evaluation  
74 of the compatibility with the substrate, the color variations, and the permanence of  
75 the vapor permeability. A further step of the research will include the assessment of  
76 the durability of the system substrate/polymer through accelerated aging cycles  
77 varying temperature, relative humidity, and solar irradiance and also the investi-  
78 gations on the real site.

### 79 3 Case Study

#### 80 3.1 *Città Studi, Sustainable Campus; Monitoring* 81 *the Klinker Facades*

82 The case study here presented is a building inside the “Leonardo Campus,”  
83 Politecnico di Milano, see also Fig. 1, on which the researchers assessed the state of  
84 conservation within the research “Città Studi, Sustainable Campus.”<sup>1</sup> The Campus  
85 is representative of many typologies of contemporary buildings. The study case has  
86 an exterior cladding system of tiles. The facades materials, exposed to excessive  
87 rainwater infiltration or critical moisture content, show a visible damage and have a  
88 consequent reduction of their durability. Scientific literature reports the prediction  
89 about exterior finishing and cladding systems service life and the use of degradation  
90 models (Sousa 2008; Emídio 2012). In each case study, the phase of diagnostic  
91 knowledge represents an essential step aimed at the definition of the correct  
92 strategies of intervention to prevent the occurrence of failure and maintain, manage,  
93 and valorize the building components.

94 The researchers developed and validated the investigative procedure on some  
95 buildings with tiles cladding systems (buildings *n* 12, 14, 15, see Fig. 1), and later,  
96 they applied the procedure on buildings with plaster finishing (buildings *n* 1, 2, 3).

---

<sup>1</sup><http://www.campus-sostenibile.polimi.it/home>.

**Fig. 1** Map of Leonardo Campus



97 Stoneware tiles cladding is a diffused rendering practice in Italy since the 1950–  
 98 1960s, due to the good wear resistance, high temperatures stability, hardness,  
 99 tenacity, and thermal inertia. Moreover, the durability of the ceramic materials, their  
 100 low cost, and low sensitivity to the effects of pollution are some of the reasons of  
 101 their application in the middle-southern region of Europe (Velosa et al. 2011). After  
 102 50 years of usage, the façades present a severe decay pattern, such as delaminations,  
 103 missing tiles, and discoloration; this is due to the action of atmospheric agents, loss  
 104 of adherence at the interfaces tile/mortar/support, and the absence of a correct  
 105 maintenance. Giò Ponti, one of the most famous architects of 1950–1980s, designed  
 106 some buildings in the Campus, and at present, their facades urgently require  
 107 maintenance. The assessment of these façades is an important issue both for the  
 108 economic aspects related to the costs of maintenance and for the repair project that  
 109 deals with contemporary buildings having high historical–artistic value. From this  
 110 side, preserving the authenticity of the building is a critical issue. At the current state  
 111 of the debate, restorers generally accept that the repair should be clearly identifiable  
 112 from a short distance. On the contrary, a “mimetic” solution, with the substitution of  
 113 materials and elements with new ones “à l’identique,” is a practice that does not fit  
 114 the conservation requirements. Therefore, the need to limit as much as possible the  
 115 substitution rises up, preventing the damage by reducing the risk factors (environ-  
 116 nment, building techniques, use, lack of maintenance, etc.) by monitoring the  
 117 degradation phenomena evolutions, and by means of a conservation plan.

118 Delamination, as defined by ICOMOS glossary (International Scientific  
 119 Committee 2008), is the detachment process affecting laminated stones. It

120 corresponds to a physical separation into one or several layers following the natural  
 121 cleavage present in the stone. This definition, applied to artificial stone materials as  
 122 mortars or cladding systems, regards the adhesion defects, and after that, decay  
 123 mechanism creates an air gap at any interface.

124 The most frequent cause regards infiltrations inside the structure, the water  
 125 evaporation, and the crystallization of soluble salts inside the pore matrix. The  
 126 growth of salts inside the finishing causes the detachment of the exterior layers due  
 127 to the mechanical stress.

128 Therefore, it is important to localize and map the presence of these defects for  
 129 the activation of maintenance. The assessment costs mainly depend on renting  
 130 elevators/forklift truck or scaffolding; therefore, the use of remote testing, that does  
 131 not require to touch the surface, implicates a strong reduction of costs.


132 Infrared thermography (IRT) techniques fully proved to be suitable at this aim  
 133 (Maldague 2001).

134 IRT monitoring allows to check the results also after the repair, through moni-  
 135 toring and assessment of new delaminations.

136 This technique has already shown its critical points. The presence of chromatic  
 137 alterations on the façade, obstructions and shades, different reflectance, and local  
 138 lacks of homogeneities can mislead the pathologies identification.

139 The use of IRT can be at transient or steady-state conditions: in the case of  
 140 adhesion problems, it is fundamental to create a temperature transitory to visualize  
 141 the map of the state of adhesion on the façade (Caglio et al. 2011; Ludwig et al.  
 142 2012). With this procedure, it is possible to evaluate a thermal gradient between  
 143 sound and detached areas. Natural or artificial sources of heating successfully  
 144 generate the proper thermal gradient for detecting the delamination. The researchers  
 145 validated the results also by numerical simulation through WUFI® software (De  
 146 Freitas et al. 2014) (Fig. 2).

**Fig. 2** Distribution of the characteristic thermal gradient due to detachment in tiles cladding systems as a function of the orientation

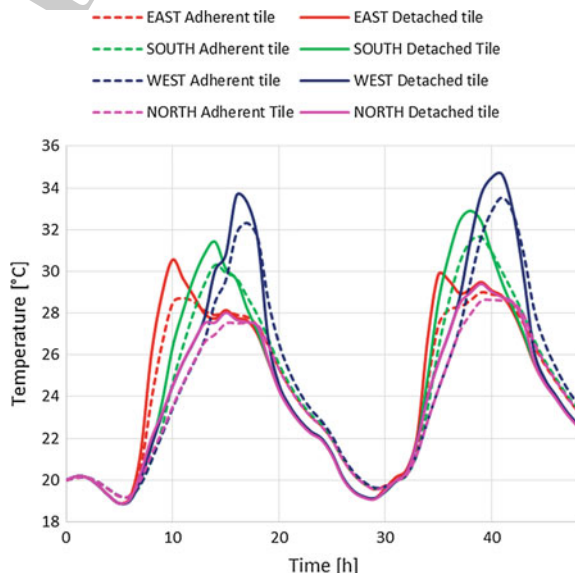

### 3.2 Description of Building 12 and Diagnostics of the State of Conservation

Building 12 has an exterior stoneware tiles cladding (Fig. 3, left). The ceramic elements, flamed at high temperature (producer Italian Society of Grès, now Italcementi s.p.a.), are no longer under production. The body of the material is compact, and the superficial layer presents the typical glaze obtained through a vitrification while firing; the glaze thickness is around 50  $\mu\text{m}$ , except for the corner tiles where it is enhanced at 150  $\mu\text{m}$  (Fig. 3, right). The underneath layer is a cement mortar bedding 4 cm thick.

IRT was used after 2 h of solar heating on Building 12. The thermal anomalies due to clinker tile delaminations were the target of the investigation.

This time span permitted to obtain the better contrast between delaminated areas and sound ones.

Cladding thickness and thermal characteristics, the presence and depth of defects, and environmental conditions (air T and RH, wind speed, solar irradiance) play a prominent role in the heat diffusion through the cladding itself.

As a result of the surveys phase, a series of pathological failures have been listed and classified according to the associated damage. The most spread and severe damage resulted the detachment, since it represents a source of danger in particular in the case of public buildings, such as a university; hence, the delamination requires a timely intervention for safety reasons (Re Cecconi 1996).



**Fig. 3** Building 12 in Campus Leonardo (left); details of the tiles of Building 12 (right)

168 Incorrect design and application are supposed to cause the majority of detach-  
169 ments and missing tiles. The areas where design errors caused the damages are  
170 mainly located close to the windows: the loss of adherence could be due to water  
171 infiltrations through the sill and the mullions, in the junction between the wall and  
172 the window frames. Rainwater can remain stagnant at the top of the window frames,  
173 because of the profile insufficiently leaning, causing the corrosion of the steel  
174 frames. Execution errors mainly deal with the mortar and to its high thickness  
175 (around 3–4 cm) where the several layers are not always adherent to each other's.

176 Cracking are also supposed to be mainly related to unsuitable design and  
177 application, because of the excessive shear stresses between tiles and support (due  
178 to the lack of the expansion joints) and the wrong choice and laying of the adhesive  
179 and substrate.

180 In addition to the IRT scanning and thermal analysis, the researchers completed  
181 the diagnostics by analyzing some samples of the facades materials and their decay  
182 products. Microscopic observations confirmed that the body of the tile is a compact  
183 ceramic material, very similar to earthenware, and the tiles have a finishing glazed  
184 layer; corner tiles do not differ from the others. EDS analyses of mortar samples  
185 resulted a common cement binder and sand as aggregate.

## 186 **4 Moisture and Protective Treatments**

### 187 **4.1 Moisture Transport Mechanisms and Damages**

188 The penetration of water in the structures causes a general decrease of their  
189 mechanical performances, depending on the absorption ability of the materials and  
190 their level of soaking (Coppola 1996). The causes of damage range from mobility  
191 of soluble salts, their crystallization inside the pores structure, freeze and thaw  
192 cycles, hydric expansion, and biological growth. Damage is located mainly on the  
193 surfaces (exfoliation, pulverization, efflorescence); otherwise, it can reach the bulk,  
194 causing cracks even across the section of the walls depending on the time of  
195 weathering exposure, the typology of building material, and the thickness of  
196 masonry. National and international standards provide the appropriate procedures to  
197 measure the specific parameters, which are helpful to evaluate the physical decay  
198 mechanisms and kinetics. In fact, the source of water infiltrations, their path into the  
199 structure, and their transport cycles in a short time determine the potential  
200 increasing of the existing damage.

201 Because of the previous surveys and analysis, the researchers chose two cement  
202 mortars (CEM I and IV) for bedding and prepared 36 specimens (18 of each type;  
203 dimensions  $5 \times 5 \times 2$  cm) for the laboratory investigations.

## 4.2 Consolidation and Protective Treatments

The use of consolidation and water-repellent treatment on natural stones is well known (Toniolo et al. 2002; Tsakalof et al. 2007). Many different organic compounds have been used as coatings for building materials (Horie 1987; Amoroso and Camaiti 1997) such as natural and synthetic waxes, acrylic resins, siloxanes perfluoropolyethers, fluorinated polyolefin, and fluoroelastomers. These different polymeric materials have been often used without an adequate knowledge of the properties of the polymer/stone system; therefore, the application did not reach an optimal formation of the final system. As a result, the treatment resulted not satisfactory for the insufficient protection effectiveness and/or the permanence on the substrate.

The term protective treatments identifies a range of products, materials, and structures, which play a defense action on building components against natural weathering or human actions. Systems, materials, and procedures can achieve the protective function, based on both active and passive interventions. The passive protection prevents the beginning of a process of degradation, acting on the causes of the degradation and/or around the component. This category includes screens, roofs or barriers (provisional or definitive), canopies, flashings, and overhangs. The active protection consists in the application of products on the surface to improve (reach) the water repellency of the protected matter. Hence, the protective treatments seek to slow the probability of transformations of the materials, because of aggressive external agents transported by water and imbalance with the surrounding environment.


In some cases, the protective products display properties similar to those of the ones under protection; nevertheless, their first requirements is to ensure water repellency and water vapor permeability.

The water repellency reduces the absorption of water into the material porosity. A good permeability allows the water vapor to pass through the material, avoiding any “barrier effect” which should accumulate water in a localized area.

### 4.2.1 Siloxane Treatments

Among the different protective products available on the market at present, the experimentation focuses on siloxanes, which are used since 1960 on natural stone; despite the application since a long time, less investigation focused on their application on artificial materials (Maravelaki-Kalaitzaki 2007; Allen et al. 1992). Siloxanes are organosilicon compounds; they form usually the backbone of the so-called silicones, and they are able to impart water repellency when applied to any surface. They show their chemical stability due to the Si–O bond. Once cured, they abate the penetration of water inside the pore structure, allowing a good water vapor permeability. Moreover, they are stable at atmospheric agents and do not change the substrate color, and they are not toxic. Nevertheless, there are also negative aspects,



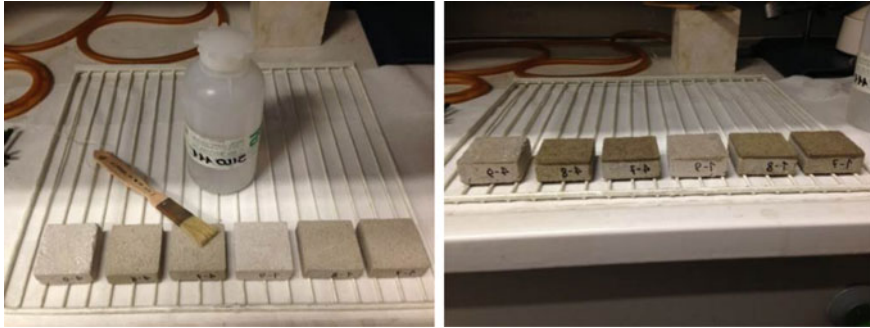

**Fig. 4** Application of the water-repellent siloxane treatment on the outer surface of cement mortar samples (CEM I and IV)

244 among which the scarce durability in the presence of sulfur dioxide (Mavrov 1983).  
 245 The researchers chose the product CTS SILO 111, which substituted the less recent  
 246 CTS 111, due to its common use in the restoration field (Fig. 4). Moreover, a vast  
 247 bibliography exists, and it supports the study of its performances in several different  
 248 conditions, comparing their performances with the ones of other products.

249 Different parameters affect the choice of a protective treatment:

- 250 – water-repellent effectiveness,
- 251 – chemical inertia with respect to the substrate,
- 252 – long-lasting vapor permeability,
- 253 – resistance to thermo-hygrometric variations,
- 254 – heat resistance,
- 255 – UV aging resistance, and
- 256 – penetration ability.

257 Erba (2015) refers about many investigation on the water-repellent effectiveness  
 258 through a series of laboratory tests and computer-based simulations, the compati-  
 259 bility with the substrate and the chromatic alterations, and the permanence of the  
 260 vapor permeability after the application of the product, all evaluated at the so-called  
 261 time  $t_0$  (after the curing of the polymeric treatment). In the following, the authors  
 262 present and discuss the results of the laboratory tests and simulations.

### 263 **4.3 Treated Mortars Properties for the Protection** 264 **of Humid Walls**

265 According to the German standard DIN4108-3 (Künzel et al. 2004), adequate  
 266 plaster and protective layers for the protection of humid walls must present the  
 267 following properties:

- 268 – water vapor diffusion-equivalent air layer thickness ( $S_d$ ) lower than 2 m,
- 269 – water absorption by capillarity ( $A$ ) lower than  $0.5 \text{ kg/m}^2 \text{ h}^{0.5}$ , and
- 270 – product of  $S_d$  and  $A$  lower than 0.2.

271 To fulfill these requirements, the authors tested different mixture for mortars by  
272 performing absorption tests such as the absorption by capillarity and the water  
273 vapor transmission tests. After this first step, they placed on the mortars' surface a  
274 water-repellent polymeric liquid treatment, and the tests were repeated.

## 275 **5 Experimental Setup, Tests for the Characterization** 276 **of Water Transport Phenomena, and Radiation** 277 **Properties of Treated/Untreated Samples**

278 The first step of the experimental research concerned the characterization of the  
279 water transport phenomena. The specimens for each type of mortars, having  
280 dimensions  $5 \times 5 \times 2$  cm, were tested before and after the application of the  
281 protective treatment. The second part reports the results of the color and solar  
282 spectral reflectance test.


283 List of the laboratory tests:

- 284 – hygroscopic absorption (UNI EN 12571),
- 285 – water absorption by capillarity (UNI EN 15801),
- 286 – water absorption by partial immersion (UNI EN ISO 15148),
- 287 – long-term water absorption by immersion (UNI EN 12087),
- 288 – water vapor transmission (UNI EN ISO 12572), and
- 289 – color measures (UNI EN 15886).

290 In the following, the paper shows the adopted procedures and the results for the  
291 tests, underlying the differences between untreated and treated samples. In fact,  
292 after the first phase without the treatment, the researchers repeated the tests on the  
293 samples with SILO 111 CTS in white spirit 10 %, (applied by brush until reaching  
294 the condition of surface saturation). They left the specimen at laboratory conditions  
295 ( $T 22 \pm 3$  °C;  $RH 50 \pm 10$  %) for 30 days to guarantee the complete curing of the  
296 polymeric product, according to the UNI 10921.

### 297 **5.1 Hygroscopic Absorption**

298 The absorption test was executed in a climatic chamber, according to UNI EN ISO  
299 12571 (2001) (Daniotti et al. 2014a, b) (Fig. 5). The researchers could not obtain  
300 the sorption curve values at relative humidity  $>90$  % due to the technical features of  
301 the climatic chamber. The missing values will be obtained in the following part of

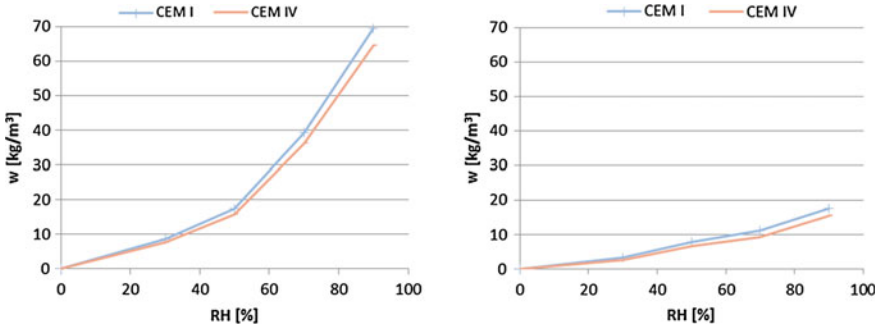

B & W IN PRINT


**Fig. 5** Relative humidity–moisture content mass by volume (untreated specimens: *left*; treated specimens: *right*)

302 the research, through long-term water absorption by immersion (UNI EN 12087  
303 thermal insulating products for building applications).

304 Observing the curves is possible to remark the reduction of the moisture content,  
305 due to the presence of the product: the tests performed on the specimens resulted  
306 with a high difference, and the moisture content decreases from around 70 to  
307 20 kg/m<sup>3</sup>.

### 5.2 Water Absorption by Capillarity

309 The researchers determined water absorption by capillarity applying the standard  
310 UNI EN 15801 (2010) (Fig. 6).

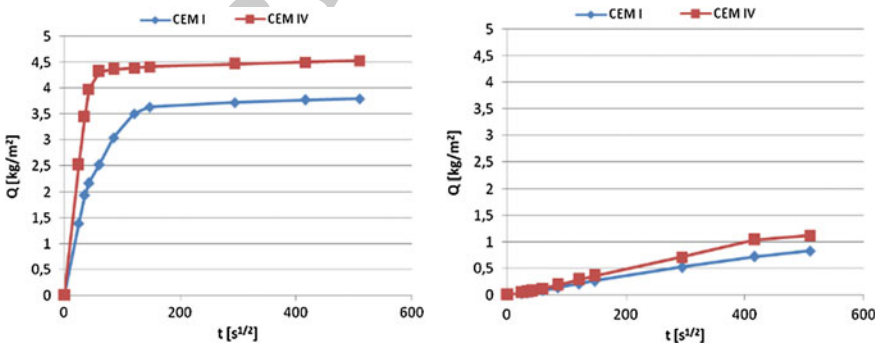

B & W IN PRINT

**Fig. 6** Curves of capillary water absorption for cement mortars (untreated specimens: *left*; treated specimens: *right*)

**Table 1** Capillary water absorption coefficient for the mortars specimens (untreated–treated)

Type of mortar	AC ( $\text{kg/m}^2 \text{s}^{0.5}$ ) before treatment	AC ( $\text{kg/m}^2 \text{s}^{0.5}$ ) after treatment	$\Delta$ AC ( $\text{kg/m}^2 \text{s}^{0.5}$ ) before–after treatment
CEM I	0.065	0.002	0.063
CEM IV	0.100	0.003	0.097

311 The diagrams show that the siloxane treatment causes an abatement of the  
312 absorbed water. Table 1 shows the value of the absorption coefficient for the  
313 different mortars.

314 It is possible to notice that for both the mortars, the coefficient decreases from  
315 untreated to treated mortars. The test result on CEM IV shows the highest reduction  
316 in terms of AC value.


### 317 5.3 Water Absorption by Partial Immersion

318 The researchers compared the water absorption values obtained by capillarity and  
319 by partial immersion, determining the water absorption coefficient by partial  
320 immersion, according to the UNI EN ISO 15148, 2003. The samples were sealed  
321 with a sealant to prevent bypassing of the coating.

322 The main interest of this test was to find out the differences between the AC  
323 value and  $A_w$  value, since the thermo-hygrometric simulations in WUFI require the  
324 results from partial immersion tests.

325 Figures 7 and 8 show a faster absorption of water (see the darker color of the  
326 surface) in the specimens of CEM I with respect to the ones of CEM IV. After  
327 40 min, the water reaches the outer surface.

328 The water absorption by partial immersion showed results very similar to those  
329 performed through capillary tests. The curves have the same trend, and the

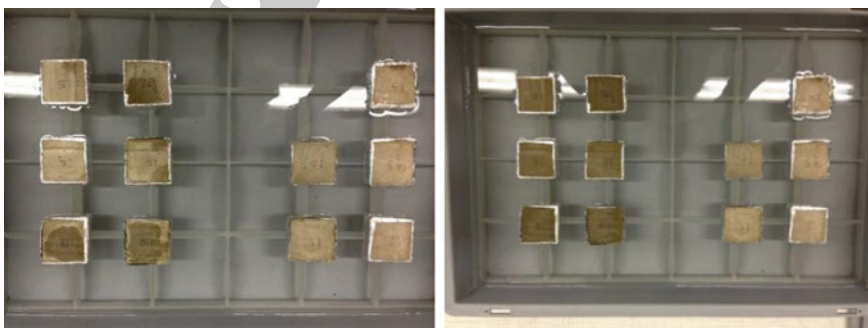


**Fig. 7** In each photo, the samples on the *left* of the basin are untreated, and those on the *right* are treated. In the photo on the *left* CEM I specimens after 5 min and in the photo on the *right* after 40 min


330 application of the water-repellent treatment reduces the water absorbed from 5–  
 331 6 kg/m<sup>2</sup> to 1–2 kg/m<sup>2</sup> (Fig. 9).

332 Table 2 shows the values of the water absorption coefficient for the two cement  
 333 mortars. Table 3 shows the differences in terms of water absorption coefficient  
 334 between the values obtained by capillarity and by partial immersion.

335 The coefficients obtained by partial immersion are always higher than those  
 336 obtained by capillarity. This is probably because the specimens' surfaces are

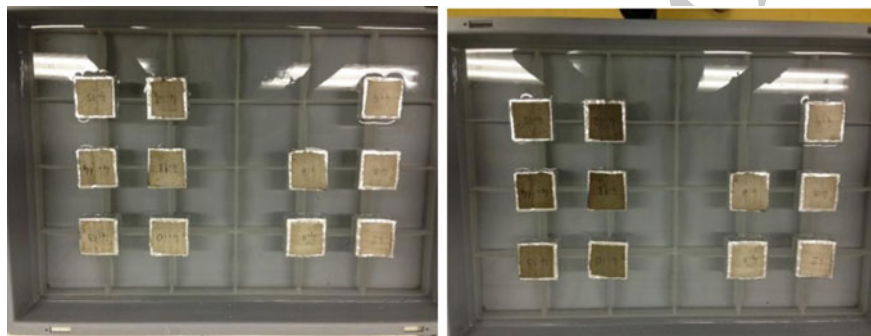

**Fig. 8** CEM IV specimens after 5 min (*left*) and after 40 min (*right*); the samples on the *right* in each picture are treated, and those on the *left* are untreated

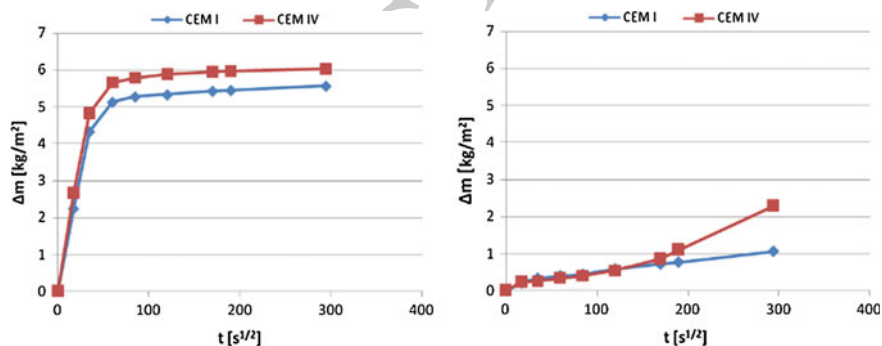

**Fig. 9** Curves of water absorption by partial immersion for cement mortars (untreated specimens: *left*; treated specimens: *right*)

**Table 2** Water absorption coefficient by partial immersion for the mortars specimens CEM I and CEM IV (untreated–treated)

Type of mortar	$A_w$ (kg/m <sup>2</sup> s <sup>0.5</sup> ) before treatment	$A_w$ (kg/m <sup>2</sup> s <sup>0.5</sup> ) after treatment	$\Delta A_w$ (kg/m <sup>2</sup> s <sup>0.5</sup> ) before–after treatment
CEM I	0.125	0.003	0.122
CEM IV	0.139	0.005	0.134

**Table 3** Differences between the water absorption coefficients by capillarity/partial immersion for the mortars specimens (untreated–treated)

Type of mortar	Aw (kg/m <sup>2</sup> s <sup>0.5</sup> ) before treatment	Aw (kg/m <sup>2</sup> s <sup>0.5</sup> ) after treatment	AC (kg/m <sup>2</sup> s <sup>0.5</sup> ) before treatment	AC (kg/m <sup>2</sup> s <sup>0.5</sup> ) after treatment	ΔAw-AC (kg/m <sup>2</sup> s <sup>0.5</sup> ) before treatment	ΔAw-AC (kg/m <sup>2</sup> s <sup>0.5</sup> ) after treatment
CEM I	0.125	0.003	0.065	0.002	0.060	0.001
CEM IV	0.139	0.005	0.100	0.003	0.039	0.002

Aw water absorption coefficient by partial immersion

CA water absorption coefficient by capillarity


337 directly in contact with water in the test of absorption by partial immersion, while in  
338 the test by capillarity, there is a layer of interposed paper. The differences between  
339 the two coefficients are negligible when considering treated samples, while for  
340 untreated samples, in particular for CEM I, the difference is quite significant.

#### 341 5.4 Determination of Water Vapor Transmission Properties

342 The researchers tested the specimens following the standard UNI EN 15803, 2010,  
343 after the desiccation at 60 °C until reaching constant mass, to avoid alterations,  
344 especially once applied the water-repellent treatment (Fig. 10).

345 Table 4 shows the results of the mean values of water vapor resistance factors for  
346 the different types of mortars before and after the application of the siloxane  
347 product.

348 It is possible to notice that the values with and without the water-repellent  
349 treatment are almost equal, and therefore, the application of the product SILO 111  
350 on cement samples does not add resistance to the flow of vapor.

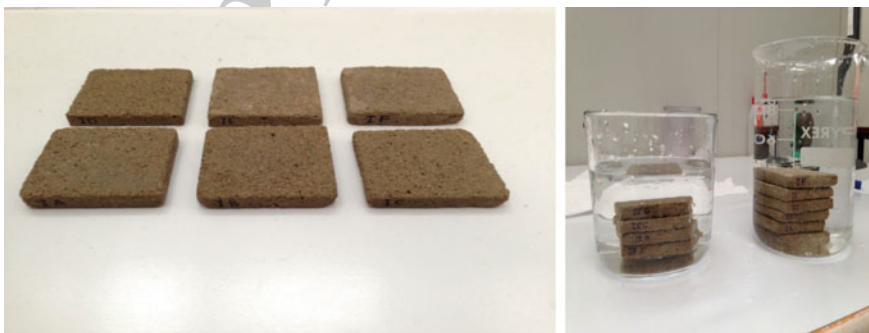

**Fig. 10** Preparation of the sample for the evaluation of water vapor transmission properties: The images shows the cement samples placed in a container of deionized water

**Table 4** Water vapor resistance factor for untreated/treated samples

Type of mortar	$\mu$ [-] before treatment	$\mu$ [-] after treatment
CEM I	13	14
CEM IV	10	12

### 5.5 Determination of Long-Term Water Absorption by Immersion

The determination of long-term water absorption by immersion has been performed following the standard UNI EN 12087, 2013.

The researchers studied the coefficient of long-term water absorption by immersion only for untreated cement samples. The long-term water absorption by total immersion is determined by measuring the change in mass of the test specimen, totally immersed in water, over a period of 28 days (Table 5).

Figure 11 shows the long-term water absorption by total immersion.


### 5.6 Color Test


The color measurement has the aim to evaluate the chromatic alterations caused by the application of the water-repellent treatment SILO 111 on the mortar specimens.

The researchers carried the measures out according to the standard UNI EN 15886, 2010. The method is based on the reflectance measures, which express the color as a number. Colors are represented in a solid or “color space” in which each point is univocally defined by three spatial coordinates to which correspond a defined color of the visible spectrum.

**Table 5** Long-term water absorption value  $W_f$  by total immersion

Specimen	$W_f$ (kg/m <sup>3</sup> )
CEM I	224.7
CEM IV	260.7

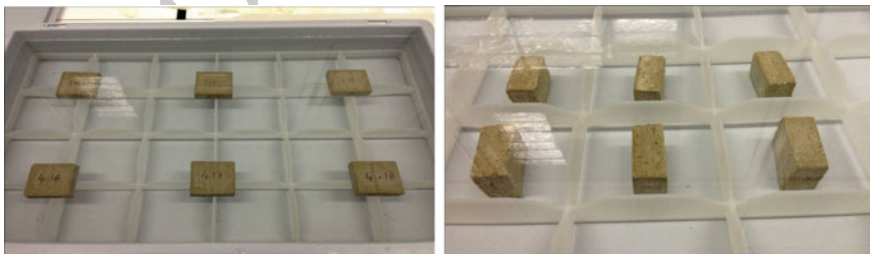**Fig. 11** Long-term water absorption performed on cement samples

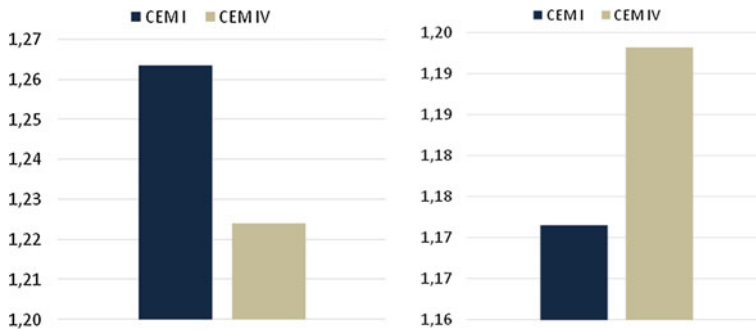

**Fig. 12** Total color difference  $\Delta E$  (left) and total shade difference  $\Delta H$  (right) between the two cement types

In this test, the system of measurement of the color is the CIE  $L^*a^*b^*$  (1976) according to the Commission Internationale de l'Éclairage (1931). The system is based on the mathematical transformation of the CIE space in a three-dimensional Euclidean space.

The variable  $L^*$  represents the measure of the brightness in a range from 0 to 100;  $a^*$  and  $b^*$  are the coordinates of the point of color in a Cartesian plane. Their values can be positive or negative, or can be equal to zero for both values for a neutral color (white, gray, black). The measurement was taken with a colorimeter Minolta Cr-200. The test procedure involves 25 measures for each specimen. The values of  $L^*$ ,  $a^*$ , and  $b^*$  are the mean values of the 25 measures, taken to minimize the error due to the presence of chromatic irregularities on the surfaces of the specimens (Fig. 12).

The diagram shows that the application of the water-repellent treatment does not affect the surface color ( $\Delta E$  ranging from 1.20 to 1.30). In fact, values around 1 are considered very good and not perceivable by naked eye.

## 5.7 Solar Reflectance

Spectrophotometry is the quantitative measurement of the reflection or transmission properties of a material as a function of the wavelength. The study aims to investigate the changes in reflection of mortars when the siloxane treatment is applied. The following graph of absorption versus wavelength (spectrum) presents the results on untreated and treated cement mortars specimens.


The solar reflectance tests follow the standard ASTM E903-12 (2012). The researchers selected 20 cement specimens CEM I and 20 cement specimens CEM IV: specimens 1.2–1.6 and 4.2–4.6 have a siloxane treatment, while from 1.10 to 1.21 and from 4.10 to 4.21 are untreated. For each specimen, two measures have been carried out. The spectral reflectance was measured with a Perkin-Elmer Lambda 900 Spectrophotometer.



395 The machine was equipped with a 150-mm Spectralon-coated integrating sphere,  
 396 a photomultiplier tube, and lead sulfide detectors. The authors measured the  
 397 reflectance and compared the measurements to a Spectralon-calibrated reference in  
 398 the 300–2500-nm wavelength range with a spectral resolution of 5 nm (Paolini et al.  
 399 2014). Two points of each sample lit by the measurement beam were used for the  
 400 analysis; thus, the surface variations were considered. For each cement type of  
 401 mortar (untreated–treated, CEM I–IV), the researchers computed the average  
 402 spectral curve and then the integrated values.

403 Focusing on the spectral data, the portions of the solar spectrum where the  
 404 treatment has the largest impact on the variations in reflectance can be determined  
 405 (Fig. 13).

406 The main differences between CEM I and IV are visible at NIR; nevertheless, in  
 407 general, the distance among the curves is constant along all the wavelengths. The  
 408 trend of the measures of untreated and treated specimens is almost equal at NIR and  
 409 becomes evidently different at VIS and UV, where it decreases for both the types of  
 410 cement.

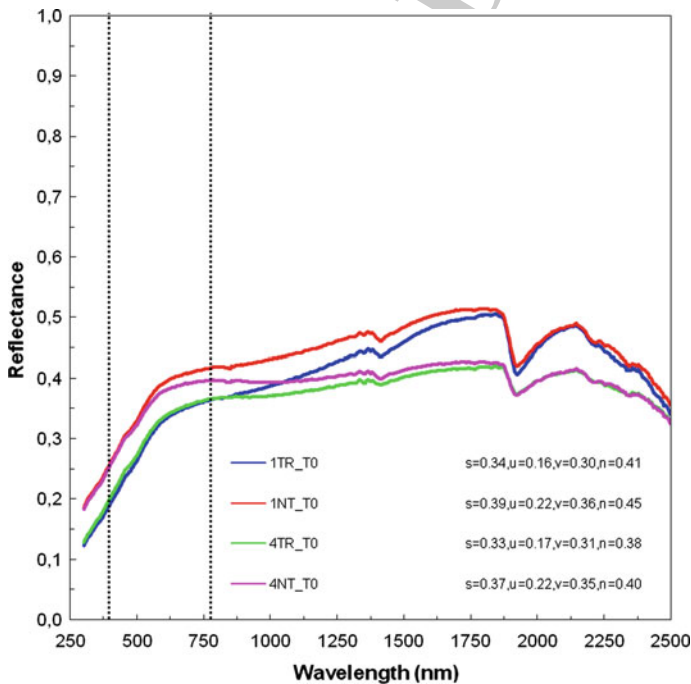

**Fig. 13** Spectral and computed solar (*s*), UV (*u*), visible (*v*), and near infrared (*n*) reflectance performed before exposure; the curves of the specimens with siloxane treatment are TR, whereas the untreated are NT

## 6 Heat and Moisture Transfer

The research has shown that the conservation of historic building facades is closely linked to the moisture control and to the water transfer inside the components. An adequate evaluation of these factors is unavoidable to produce accurate and timely interventions. However, the experiments in laboratory and on-site are time- and money-consuming, and the possibility to trust on computer-based simulations would be useful and would guarantee savings (Künzel 1995; Krus 1996).

For this reason, the last part of the research deals with the validation of the results through computer simulations and the development of a set of data for the investigated building materials, and in particular, cement mortars evaluated with a water-repellent protective treatment.

The researchers used the program WUFI (Wärme und Feuchte instationär—Transient Heat and Moisture), developed by Fraunhofer Institute for Building Physics. It allows the use of data derived from outdoor and laboratory tests for the development of realistic simulations of the transient hygrothermal behavior of building materials and components, exposed to natural climate conditions.

The first step for the assessment of moisture transfer by numerical simulation has been the search through laboratory tests of the necessary material data set, which have been evaluated according to the standard UNI EN 15026 (2008). The thermo-hygrometric characterization of the mortars performed in laboratory and on site supported the simulations with the specific data of the materials of the analyzed case studies. However, during the simulations, the researchers used also the data of materials already existing in the database to catch the differences and understand the influence of the characterization data on the results. Moreover, they referred to the database for the characterization of the other materials composing the walls, which did not go under investigation in this research.

The specific boundary conditions have been referred to Milan and compared to the available data. The dynamic simulations are fundamental in case of the external layer evaluation, which is directly affected by the microclimatic variations occurring in the environment (Marra 2011).

Aim of the simulation was to support the choice of the best formulation in terms of compatibility and moisture absorption, simulating the behavior of the two mortars mix design with/without the application of the water-repellent treatment. For the sake of the research, the authors considered only the stratigraphy in correspondence with the mortar joints, and therefore, the model of the hygrothermal behavior of the components has been performed using WUFI-1D. A further development of the study implies 2D simulations especially in the case of tiles cladding systems, where the two sections of the finishing (mortar joints/tiles and embedded mortar) contribute in a different way to the final moisture balance of the façade.

The researchers investigated the northern façade of Building 12, Campus Leonardo, and in particular focused the simulations on the bedding mortar layer. In fact, the thermographic analysis performed on the elevation underlined the presence

454 of adhesion problems distributed on the external cladding system. They assume a  
 455 constant geometry of the mortar layer without swelling and shrinkages.

## 456 6.1 Material Properties and Boundary Conditions

457 According to the standard UNI EN 15026, 2008, Table 6 shows the list of the  
 458 material properties, which are necessary for the simulations. The list of the  
 459 hygrothermal properties are for both untreated and treated materials, according to  
 460 the laboratory tests availability. The tests described in the previous paragraphs  
 461 provided the measured values, which correspond to the following:

- 462 – bulk density  $\rho$  ( $\text{kg/m}^3$ ).
- 463 – moisture storage function (sorption curve)  $w\phi$ , according to the UNI EN ISO  
 464 12571, 2001.
- 465 – diffusion resistance factor  $\mu$ . For the sake of the research, aimed at evaluating the  
 466 permanence of the vapor permeability by the treatment, the researchers followed  
 467 the standard UNI EN 15803, 2010. Actually, the values used for the simulations  
 468 in WUFI are those obtained by dry-cup tests, according to the UNI EN ISO  
 469 12572, 2006. For these reasons, the measured values were verified with tabu-  
 470 lated ones (ISO 10456 2007) and performed a sensitivity analysis. The values  
 471 are comparable and do not affect the final results.
- 472 – liquid conductivity  $K$  that has been determined by the approximations using the  
 473 water absorption coefficient by partial immersion (UNI EN ISO 15148, 2003).  
 474 Moreover, the differences between the coefficients by partial immersion and  
 475 capillarity observed for cement mortars appear not significant, especially for  
 476 treated samples. For this reason, the researchers decided to use the values  
 477 obtained from water absorption by capillarity test.

**Table 6** Material data set  
 and properties used in the  
 simulations

	CEM I	CEM IV	
$\rho$ ( $\text{kg/m}^3$ )	1928	1867	Measured
$\varepsilon$ ( $\text{m}^3/\text{m}^3$ )	0.3	0.3	Tabulated
$c_p$ ( $\text{J/kg K}$ )	850	850	Tabulated
$\lambda$ ( $\text{W/m K}$ )	1.2	1.2	Tabulated
$\mu$ [-] NT	13	10	Measured
$\mu$ [-] TR	14	12	Measured
$A_w$ ( $\text{kg/m}^2 \text{s}^{0.5}$ ) NT	0.125	0.139	Measured
$A_w$ ( $\text{kg/m}^2 \text{s}^{0.5}$ ) TR	0.003	0.005	Measured
$AC$ ( $\text{kg/m}^2 \text{s}^{0.5}$ ) NT	0.065	0.100	Measured
$AC$ ( $\text{kg/m}^2 \text{s}^{0.5}$ ) TR	0.002	0.003	Measured
$\alpha$ [-] NT	0.61	0.63	Measured
$\alpha$ [-] TR	0.66	0.67	Measured

The untreated mortars are defined as NT, whereas the treated ones as TR

- 478 – free water saturation ( $\text{kg/m}^3$ ) taken from the laboratory tests according to the  
479 standard UNI EN 12087, 2013.  
480 – shortwave (solar) radiation absorptivity [–] available for untreated cement  
481 mortars, according to the standard ASTM E903—12, 2012.

482  
483 The other parameters [porosity  $\varepsilon$  ( $\text{m}^3/\text{m}^3$ ), specific heat capacity of dry material  
484  $c_p$  ( $\text{J/kg K}$ ), and thermal conductivity of dry material  $\lambda$  ( $\text{W/mK}$ )] have been defined  
485 considering the standard ISO 10456, 2007.

486 The boundary conditions are defined in relation to the simulation to be modeled.  
487 The first analysis has regarded the validation of the laboratory test about hygro-  
488 scopic absorption, and therefore, the researchers set up the boundary conditions  
489 according to the specific temperature and relative humidity inside the climatic  
490 chamber.

491 The second set of simulations regarded the evaluation of the real behavior of the  
492 mortars, in order to verify the efficacy of the water-repellent treatment in terms of  
493 water absorption reduction.

## 494 6.2 Simulation Modeling

495 The first analysis performed with WUFI-1D has been modeling the hygrothermal  
496 behavior of the mortar specimens obtained in the laboratory, to verify the data  
497 resulted from experimental tests (Marra 2011).

498 This series of simulation has been developed considering a mortar layer 2 cm  
499 thick, which corresponds to the thickness of the mortars specimens used in the  
500 laboratory. In the case of treated surfaces, the mortar has been divided in two parts:  
501 In the first, the researchers inserted the values obtained on the treated specimens and  
502 in the second the untreated ones, since the researchers assumed that the protective  
503 treatment properties are to be considered in the first centimeter of product penetra-  
504 tion. They have defined the boundary conditions considering constant tempera-  
505 ture at 20 °C, while imposing different steps in the relative humidity, corresponding  
506 to those used in the climatic chamber during the hygrothermal absorption tests (0,  
507 30, 50, 70, and 90 %). The initial relative humidity of the component has been zero  
508 since the specimens remained in the desiccator until they reach the constant weight  
509 before the test.

510 The duration of the desiccation was two week (336 h) for the first two RH steps  
511 (30, 50 %) and of four weeks (672 h) for the remaining steps (70, 90 %).

512 In the analysis, the conditions imposed on both the sides of the samples are equal  
513 since the specimens were freely in contact with the environment inside the climatic  
514 chamber. In this case, it should be noted that in WUFI, only two surfaces are  
515 considered at the moisture balance, while in the laboratory tests also the sides  
516 contributed to the hygroscopic exchanges.

517 In the second set, the researchers simulated the presence of a plastic film, since  
 518 during the laboratory tests a plastic waterproof paraffin film sealed the boundary of  
 519 the specimens, leaving only one free surface exposed toward the environment. They  
 520 considered 3 measurement points placed, respectively, on the surface (0 m) at  
 521 0.05 m in depth and in the center of the sample (0.01 m) to monitor the trend of  
 522 relative humidity along the thickness of the layer.


523 Figure 14 shows the simulations for CEM I mortar; nevertheless, the results were  
 524 similar also for CEM IV.

525 In general, it is possible to notice that the component reaches the equilibrium  
 526 with the environment in a longer time when relative humidity is increasing.


527 Adding the waterproof layer, the time to reach equilibrium increases with respect  
 528 to the simulations considering free specimens, since the area exposed is reduced.  
 529 Treated specimens reach faster the equilibrium.

530 The second objective of the simulations was to verify the best mortar mix design  
 531 in terms of the lowest moisture absorption among those investigated. In the fol-  
 532 lowing, the researchers have performed simulations on treated mortars to verify the  
 533 effectiveness of the applied siloxane water-repellent treatment (SILO 111) (Fig. 15).

534 The graph shows a reduction of absorbed water and in the water content peaks in  
 535 the specimens treated with the siloxane product SILO 111 with respect to the  
 536 untreated mortar.

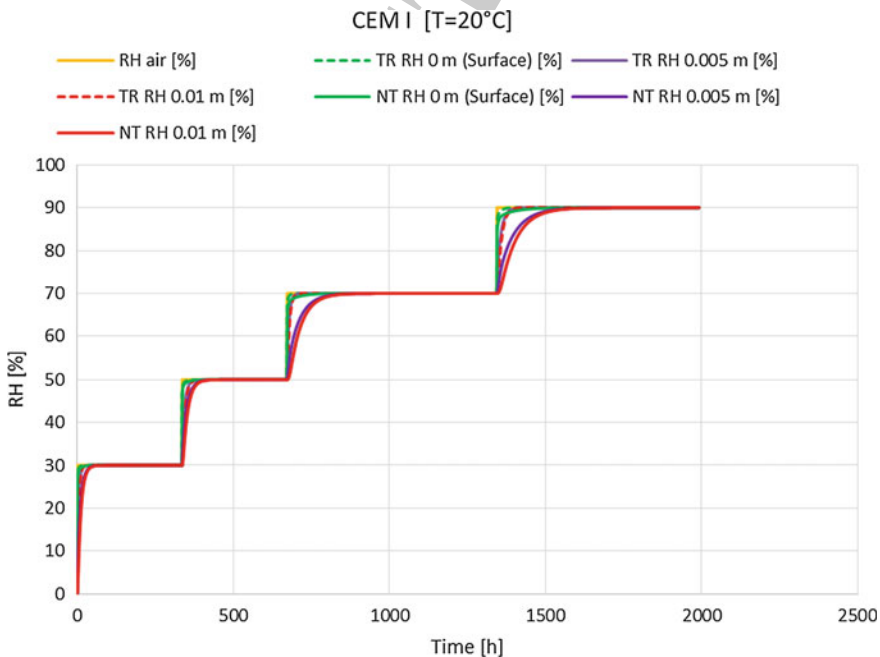

**Fig. 14** Comparison of the RH trends for untreated/treated cement (CEM I) specimens

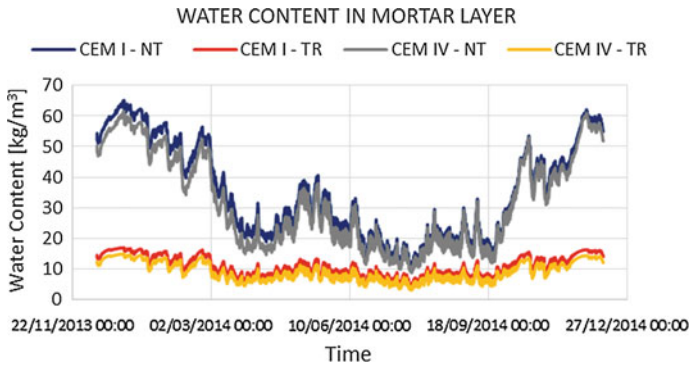

**Fig. 15** Comparison of the water content trend in the external mortar (joints-section) for treated/untreated cements specimens

537 The trend for the two cement mortar types is equal even if CEM IV shows a  
 538 higher reduction both in the treated and in the untreated curve.

539 Moreover, from the reported graphs, the dependency on the seasons of the trend  
 540 of water content is apparent in the untreated specimens: in spring/summer, it is  
 541 equal to  $20 \text{ kg/m}^3$ , while in autumn/winter, it is around  $50 \text{ kg/m}^3$ . Instead, for the  
 542 treated specimens, it is almost constant. These simulations have shown the efficacy  
 543 of the treatment in terms of absorbed water in the external mortar layer.

## 544 7 Conclusions

545 The presented work suggests a methodology for the evaluation of moisture transfer  
 546 in bedding mortar layers to improve the conservation of clinker facades. Besides,  
 547 the results of the monitoring and of the experiments provide effective indications for  
 548 the correct strategies of maintenance (Daniotti et al. 2014a, b).

549 The investigations on the application of the water-repellent siloxane treatment  
 550 SILO 111 show that the analyzed mortars fulfill the requirements necessary for the  
 551 protection of humid walls (Künzel et al. 2004). Moreover, the treatment has shown  
 552 its water-repellent effectiveness and its vapor permeability: the water vapor resis-  
 553 tance factor, obtained through the experiments in laboratory, basically, remains  
 554 constant between untreated/treated samples. Besides, it is resistant to  
 555 thermo-hygrometric variations, it does not provoke chromatic alteration on the  
 556 surfaces, and it is compatible with the substrate. The computer simulations on  
 557 moisture transfer validated the results obtained through the laboratory tests and  
 558 verified the effectiveness of the siloxane protective treatment in terms of reduction  
 559 of absorbed water.

## References

560

- 561 Allen NS, Edge MD, Horie CV (1992) *Polymers in conservation*. Royal Society of Chemistry,  
562 Cambridge
- 563 Amoroso G, Camaiti M (1997) *Scienza dei materiali e restauro*. Alinea Editrice
- 564 Amoroso GG, Fassina V (1983) *Stone decay and conservation*. Materials Science Monograph, 11  
565 ASTM E903-12 (2012) Standard test method for solar absorptance, reflectance, and transmittance  
566 of materials using integrating spheres
- 567 Caglio S, Redaelli V, Gargano M, Ludwig N, Rosina E (2011) The surfaces of contemporary  
568 architecture: characterization of clinker by IRT. In: Proceedings of 11th international workshop  
569 on advanced infrared technology and applications. L'Aquila, pp 1–10
- 570 Coppola L (1996) *Umidità nelle costruzioni: diagnosi e rimedi*. In *Presenza tecnica*, pp 79–86
- 571 Daniotti B (2009) *Building durability and maintenance*. Cusl, Milano
- 572 Daniotti B, Erba S, Rosina E (2014) Development of a methodological procedure for the durability  
573 evaluation of existing exterior finishings. In: Proceedings of XIII international conference on  
574 durability of building materials, Sao Paulo
- 575 Daniotti B, Erba S, Muioli R, Rosina E, Sansonetti A (2014) PPC at Lavello Convent: towards a  
576 sustainable conservation plan after the restoration. In: Proceedings of the PPC conference:  
577 preventive and planned conservation, Monza-Mantova
- 578 De Freitas SS, De Freitas VP, Barreira E (2014) Detection of façade plaster detachments using  
579 infrared thermography—a nondestructive technique. *Constr Build Mater* 70:80–87
- 580 Emídio FA (2012) *Dissertação par a obtenção do Grau de Mestre em Engenharia Civil - Aplicação  
581 do método factorial à previsão da vida útil de revestimentos de pedra natural*. Lisboa
- 582 Erba S (2015) *Knowledge and diagnostics for the durability of external finishing systems*. Doctoral  
583 dissertation in Building Engineering, Politecnico di Milano. Supervisor: Daniotti B, Co-Tutors:  
584 Rosina E, Sansonetti A
- 585 Horie CV (1987) *Materials for conservation*. Butterworth & Co, London
- 586 ICOMOS International Scientific Committee (2008) *ICOMOS-ISCS: Illustrated glossary on stone  
587 deterioration patterns*. Champigny/Marne, France
- 588 Krus M (1996) *Moisture transport and storage coefficients of porous mineral building materials*.  
589 Fraunhofer IRB Verlag
- 590 Künzel HM (1995) *Simultaneous heat and moisture transport in building components. One- and  
591 two-dimensional calculation using simple parameters*. Fraunhofer IRB Verlag
- 592 Künzel HM, Künzel N, Holm A (2004) Rain protection of stucco facades. In: Proceedings of the  
593 performances of envelopes of whole buildings IX conference. Clearwater Beach, Florida
- 594 Ludwig N, Rosina E, Caglio S, Gargano M, Redaelli V (2012) Heat diffusion in Klinker facade:  
595 the study case of a Giò Ponti building. *Adv Opt Technol*
- 596 Maldague X (ed) (2001) *Non destructive testing handbook, 3rd edn, vol 3: Infrared and thermal  
597 testing*. ASNT Columbus (OH), USA
- 598 Maravelaki-Kalaitzaki P (2007) Hydraulic lime mortars with siloxane for waterproofing historic  
599 masonry. *Cem Concr Res* 283–290
- 600 Marra E (2011) *Influenza dell'ambiente sulla corrosione degli inserti di acciaio nelle murature  
601 antiche*. Doctoral dissertation in building engineering, Politecnico di Milano. Tutors:  
602 Daniotti B, Bertolini L
- 603 Mavrov G (1983) Aging of silicone resins. *Stud Conserv* 28:171–178
- 604 Nicoletta M (2003) *Programmazione degli interventi in edilizia. Guida al libretto di manutenzione  
605 del fabbricato*. Maggioli Editore
- 606 Paolini R, Zinzi M, Poli T, Carnielo E, Mainini AG (2014) Effect of ageing on solar spectral  
607 reflectance of roofing membranes: natural exposure in Roma and Milano and the impact on the  
608 energy needs of commercial buildings. *Energy Build* 333–343
- 609 Re Cecconi F (1996) *Metodologie e strumentazioni per la previsione della durabilità di  
610 componenti edili per edifici scolastici ai fini della loro programmazione manutentiva*.  
611 Doctoral dissertation

- 612 Sousa R (2008) Dissertação de Mestrado Integrado em Engenharia Civil - Previsão da vida útil dos  
613 revestimentos cerâmicos aderentes em fachada. Lisboa
- 614 Toniolo L, Poli T, Castelvetro V, Manariti A, Chiantore O, Lazzari M (2002) Tailoring new  
615 fluorinated acrylic copolymers as protective coatings for marble. *J Cult Heritage* 309–316
- 616 Tsakalof A, Manoudis P, Karapanagiotis I, Chryssoulakis I, Panayiotou C (2007) Assessment of  
617 synthetic polymeric coatings for the protection and preservation of stone monuments. *J Cult*  
618 *Heritage* 69–72
- 619 UNI EN 12087 (2013) Thermal insulating products for building applications. Determination of  
620 long term water absorption by immersion
- 621 UNI EN 15026 (2008) Hygrothermal performance of building components and building elements.  
622 Assessment of moisture transfer by numerical simulation
- 623 UNI EN 15801 (2010) Conservation of cultural property. Test methods. Determination of water  
624 absorption by capillarity
- 625 UNI EN 15803 (2010) Conservazione dei beni culturali - Metodi di prova - Determinazione della  
626 permeabilità al vapore d'acqua
- 627 UNI EN 15886 (2010) Conservazione dei Beni Culturali - Metodi di prova - Misura del colore  
628 delle superfici
- 629 UNI EN ISO 12571 (2001) Hygrothermal performance of building materials and products:  
630 determination of hygroscopic properties
- 631 UNI EN ISO 12572 (2006) Hygrothermal performance of building materials and products.  
632 Determination of water vapour transmission properties
- 633 UNI EN ISO 15148 (2003) Hygrothermal performance of building materials and products:  
634 Determination of water absorption coefficient by partial immersion
- 635 Velosa A, Veiga R, Martins G (2011) Water behaviour of old and new tiles—a contribution  
636 towards the conservation of ceramic facades. In: *Proceedings of XII DBCM, Porto, Portugal*